

# MURRAY RIX

33C VAUXHALL INDUSTRIAL ESTATE  
GREG STREET, REDDISH, STOCKPORT SK5 7BR  
TEL 0161 475 0870 FAX 0161 475 0871



## TEST CERTIFICATE

### PARTICLE SIZE DISTRIBUTION

BS EN 933-1 : 2012 (Washing & Sieving Method)


Determination of water content in accordance with BS EN 1097-5:2008

CLIENT	Nick Brookes Recycling Ltd
SITE	Green Lane, Wardle, Nantwich, CW5 6DB
JOB NUMBER	MRN 3265/11

SAMPLE LABEL	MOT Type 1 - 25 & 26	DATE SAMPLED	17-Oct-18
LAB SAMPLE No	79483	DATE RECEIVED	17-Oct-18
DATE TESTED	18-Oct-18	SAMPLED BY	Client

MATERIAL	Subbase Type 1
ADVISED SOURCE	Nick Brookes Recycling Ltd ex Green Lane, Wardle, Nantwich, CW5 6DB

Sieve Size (mm)	% Passing (%)	Specification (%)	Sieve Size (mm)	% Passing (%)	Specification (%)
125	100		6.3	40	
90	100		5	37	
80	100		4	36	12-53
75	100		2	30	6-42
63	100	100	1.18	28	
50	96		1	27	3-32
40	87		0.6	25	
31.5	78	75-99	0.5	24	
28	73		0.425	22	
20	58		0.3	18	
16	52	43-81	0.25	15	
14	51		0.15	8	
10	46		0.125	7	
8	43	23-66	0.063	4.6	0-9

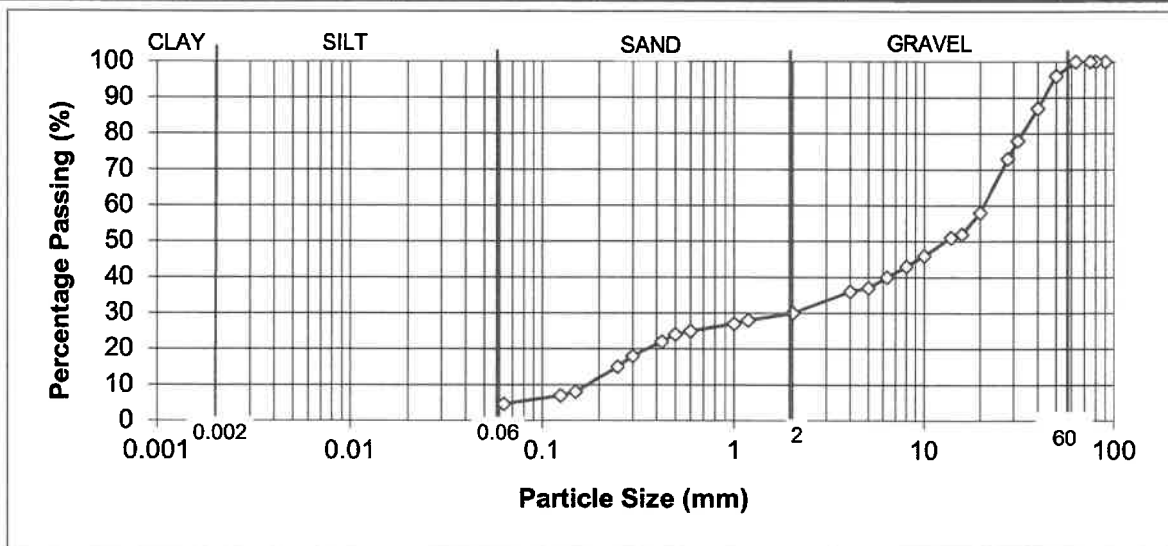

#### REMARKS

Sample complies with the advised grading specification, specification shown is the overall grading specification in accordance with the specification for highway works Feb 2016.  
Percentage of material passing 16mm and retained 8mm = 9% (Specification 7% to 30%)  
Percentage of material passing 8mm and retained 4mm = 7% (Specification 7% to 30%)

SIGNED  
NAME

O.P. Davies BA (Hons)  
(Laboratory Manger)

DATE

31-Oct-18